


TruForm™ Metal Powders for Additive Manufacturing



Making our world
more productive




TruForm™
Metal Powders

TruForm™ 718 Metal Powder

TruForm™ 718 is a precipitation-hardenable nickel-chromium alloy with excellent properties for strength, fatigue, creep, and rupture strength up to 1300°F (704°C). TruForm™ 718 is a high volume production alloy for high temperature applications such as aircraft engines and gas turbines.

Particle Size Distribution


Powders are available in a wide variety of particle size distributions and can be customized for your applications.

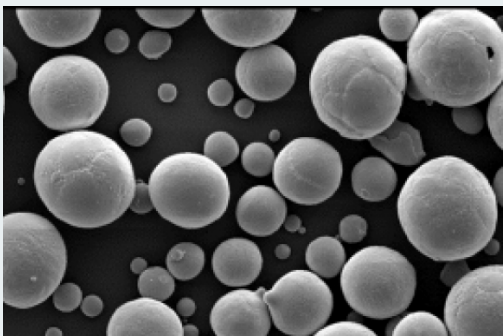

Representative SEM Image - TruForm™ 718

TruForm™ Metal Powders for All Additive Manufacturing Processes Including:

- Direct Metal Deposition (DED)
- Direct Metal Laser Sintering (DMLS)
- Electron Beam Melting (EBM)
- Laser Metal Deposition (LMD)
- Laser Powder Bed Fusion (LPBF)

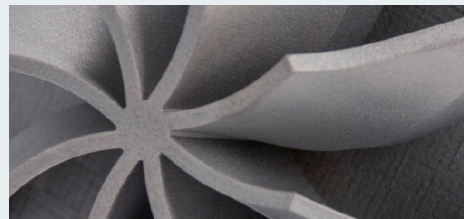

ELEMENT	TYPICAL COMPOSITION
Ni	50.00 - 55.00
Cr	17.00 - 21.00
Fe	15.00 - 21.00
Nb+Ta	4.75 - 5.50
Mo	2.80 - 3.30
Ti	0.65 - 1.15
Al	0.20 - 0.80
Co	1.00 Max
Mn	0.35 Max
Si	0.35 Max
Cu	0.30 Max
C	0.08 Max
Ta	0.05 Max
P	0.015 Max
S	0.015 Max
B	0.006 Max

Typical Mechanical Properties (contact us for additional property data)

ROOM TEMPERATURE	AS BUILT	AS BUILT MIN. ASTM F3055-14	HEAT TREAT PER ASM 5662	HT MIN. ASTM F3055-14	
Tensile Strength	(XY)	1080 ± 50 MPa 157 ± 7 ksi	980 MPa 142 ksi	1450 ± 100 MPa 210 ± 15 ksi	1240 MPa 180 ksi
	(Z)	960 ± 50 MPa 139 ± 7 ksi	920 MPa 133 ksi	1380 ± 100 MPa 200 ± 15 ksi	1240 MPa 180 ksi
Yield Strength	(XY)	800 ± 50 MPa 116 ± 7 ksi	635 MPa 92 ksi	1265 ± 100 MPa 184 ± 15 ksi	940 MPa 136 ksi
	(Z)	625 ± 50 MPa 91 ± 7 ksi	600 MPa 87 ksi	1205 ± 100 MPa 175 ± 15 ksi	920 MPa 133 ksi
Elongation	(XY)	31 ± 5%	27%	20 ± 5%	12%
	(Z)	35 ± 5%	27%	20 ± 5%	12%

TruForm™ Metal Powders for Additive Manufacturing

A Linde company



Making our world
more productive



AM Quality Lab

Our quality laboratory is NADCAP accredited and registered as an ISO-9001:2008 and AS9100 facility. We offer 100 percent lot inspection along with a certificate of analysis that details the variety of quality tests we conduct from our state-of-the-art facility. This ensures your printed products meet your performance and surface finish specifications.

Contact Us Today

Contact our technical sales team for guidance in selecting a material, requesting an alloy not listed here, or for additional details.
[praxairsurfacetechologies.com/am](https://www.praxairsurfacetechologies.com/am)

USA TruForm@linde.com

EU AME.Europe@linde.com



Powder Atomization Capabilities

Praxair Surface Technologies is a worldwide resource for fine and spherical, gas-atomized powders and a leader in vacuum induction melt argon gas atomization (VIM-AGA) technology.

We operate numerous vacuum induction melt units with Argon gas atomization and pour more than 5+ million lbs of powder each year.



Additive Manufacturing Lab

We are printing parts every day in our AM metal powder laboratory to ensure that layer by layer, you are getting a premium product that can produce products to your exacting specifications.

Praxair Surface Technologies, a Linde Company

1500 Polco Street, Indianapolis, IN 46222

Phone +1 317 240 2500, Fax +1 317 240 2255

www.praxairsurfacetechologies.com, TruForm@linde.com

© Copyright 2022 Praxair S. T. Technology, Inc., All rights reserved